


## 熔融石英ガラスの屈折率

波長/nm	N
706.519	1.455295
656.273	1.456516
587.562	1.458612
546.075	1.460227
486.133	1.463273
435.835	1.466840
404.656	1.469766
365.015	1.474691
334.148	1.479917
296.728	1.488894
253.652	1.505683
228.802	1.521319

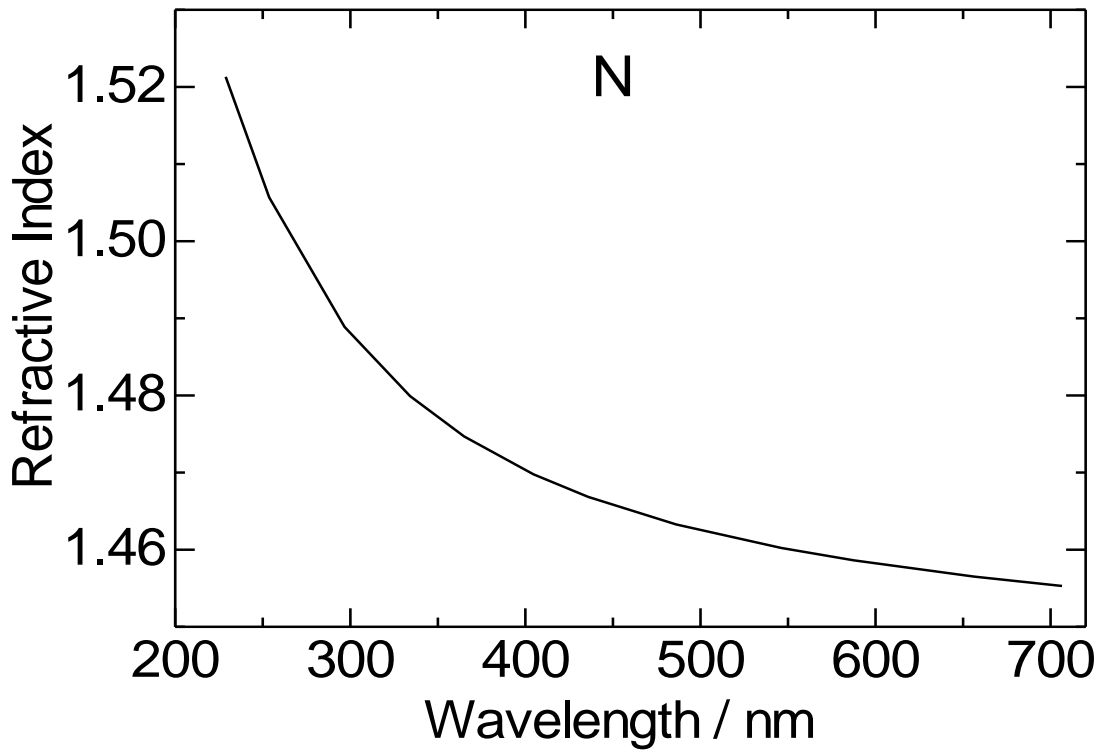

## 屈折率の波長依存性